

Original scientific paper



TiO₂/Au Nanomaterial for Photocatalytic Degradation of hormones

¹ Irena Kereković² Ivana Grčić³ Andreja Gajović¹ University of Applied Health Sciences, Department of Chemistry, Biochemistry and Clinical Chemistry, Zagreb, Croatia² Faculty of Geotechnical Engineering, Department of Environmental Engineering, University of Zagreb, Varaždin, Croatia³ Ruđer Bošković Institute, Zagreb, Croatia

visible part of the spectrum and pronounced photocatalytic activity.

Abstract

Photocatalyst based on TiO₂ nanotubes doped with Au nanoparticles was prepared and characterised. Raman spectroscopy was used for the basic characterization of the nanostructures which confirmed the anatase crystal phase of TiO₂ photocatalyst and presence of Au on the surface. The morphology of the surface on the nanoscale and chemical composition of the samples were examined with a field emission gun scanning electron microscopy (FEG-SEM) equipped with an energy dispersive spectroscopy (EDS) system with which the preparation of TiO₂NT/Au was established. The photolytic and photocatalytic degradation of estrogenic hormone 17 β-Estradiol (E2) over a wide range of wavelengths of input radiation (300-1100 nm) indicate the ability of the newly synthesized catalyst to absorb radiation of the

Key words: nanostructured TiO₂, Au nanoparticles, photocatalysis, hormones

Article received: 15.12.2022.

Article accepted: 1.4.2022.

<https://doi.org/10.24141/1/8/2/5>

Corresponding author:

Irena Kereković
University of Applied Health Sciences
Department of Chemistry, Biochemistry and Clinical Chemistry
Mlinarska cesta 38, Zagreb, Croatia
Tel: + 385 91 4595 984
E-mail: irena.kerekovic@zvuh.hr

Introduction

The manipulation of matter on a nanometre scale to produce new materials and devices has received considerable attention in the last twenty years^{1,2}. Unique physicochemical properties of nanomaterials substantially deviate from characteristics of bulk materials³. As a result, we can employ nanomaterials in various fields, such as energy conversion and storage⁴, rechargeable lithium batteries⁵, sensors⁶, etc.

Widely studied nanostructured TiO₂ with its versatile properties has proved to be a very promising material for application in dye-sensitized solar cells^{7,8}, sensors⁹, photocatalysis¹⁰, optical coatings¹¹, biomedical coatings¹² and so forth. A number of techniques are currently used for nanostructured TiO₂ preparation including chemical (template) synthesis¹³, hydrothermal synthesis^{14,15} and electrochemical anodization¹⁶⁻¹⁹. Back in 1999, Zwilling et al²⁰ demonstrated the formation of a self-ordering TiO₂ nanoporous structure by anodization in fluoride containing chromic acid. They stressed that small amount of fluoride ions in the electrolyte is crucial for the formation of self-ordering TiO₂ nanoporous structures. Following this study, many research groups have worked to optimize anodization parameters in order to develop self-ordering nanotubular arrays²¹⁻²⁸. Electrochemical anodization of titanium is a straightforward, inexpensive and direct approach of synthesizing TiO₂ nanostructures. Variation of the anodization parameters can affect the diameter, shape and density of the nanostructures²⁹⁻³¹. TiO₂ exists in amorphous form and three crystal structures, rutile, anatase and brookite. As-prepared nanoporous material has an amorphous structure, therefore thermal annealing is necessary to obtain a well-defined nanocrystalline phase³² showing better photocatalytic properties. In conventional photolytic wastewater treatment processes, TiO₂ in the form of nanoparticles is already used due to its chemical and biological inertness, significant photocatalytic activity in the UV range and reasonable prices³³. In order to extend photocatalytic activity to the visible part of the spectrum (VIS) and thus exploit more energy, the doping of TiO₂ with precious metals³⁴ such as gold (Au) has been investigated.

Rapid industrial development has led to a significant rise in the concentration of pollutants in the environment. Pollutants are different types of substances that

pose a threat to the ecosystem. In Directive 2013/39/EU³⁵ of the European Parliament and of the Council 17 β -Estradiol (E2, Figure 1), one type of steroidal estrogen was added to the list of substances that pose a threat to human health. E2 belongs to a group of endocrine-disrupting chemicals and can be found in environmental water samples and thus enter the human food chain. As E2 concentrations increase each year, monitoring and removal of quantities exceeding the maximum permitted values is required.

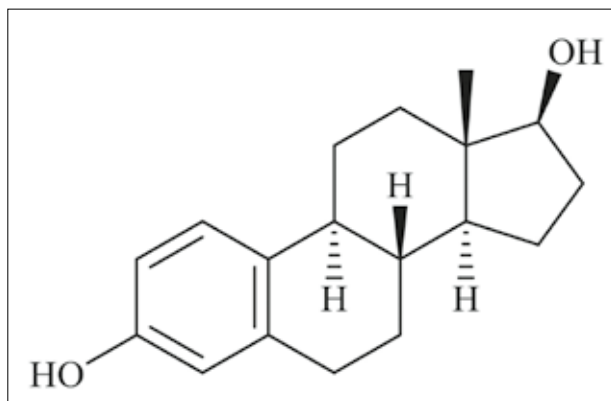


Figure 1. Chemical structure of 17 β -Estradiol (E2).

In November 2013, the European Parliament and the Council of the European Union adopted the current, seventh action program that promotes sustainable development and innovation while respecting Earth's natural resources and protecting the health and well-being of its inhabitants. The program lists nine priority objectives³⁶ and employment of renewable energy sources (sunlight) is one of them. Photocatalysis is one of the most important wastewater treatment techniques that uses a renewable energy source. It belongs to the so-called advanced oxidation processes (AOP). In these processes, highly reactive hydroxyl radicals (OH•) are formed with the help of light, which decompose organic compounds into CO₂ and H₂O with little or no secondary waste.

Adequate means to use natural resources responsibly and sustainably include improvement of existing processes and the design of new materials relevant to renewable energy. The main purpose of this study was to prepare and characterize a catalyst based on TiO₂ in the form of nanotubes (TiO₂NT) modified with Au nanoparticles (TiO₂NT/Au) and its ability to oxidize the model E2 molecule.

Materials and methods

Chemicals and solutions

Ethylene glycol (EG), ammonium fluoride (NH₄F), acetone, isopropanol, hydrogen tetrachloroaurate solution (HAuCl₄), 17 β -Estradiol (E2), formic acid and acetonitrile were obtained from Merck (Germany). All the chemicals were of analytical grade. Ultrapure water with conductivity of 0.055 μ S/cm used for electrolyte preparation was from SG Reinstwassersystem (Austria). Titanium foil of 0.25 mm thickness was from Merck (Germany).

Preparation of TiO₂NT/Au

Nanostructured TiO₂NT was prepared by anodizing Ti foil. Prior to anodizing, the Ti foil was cleansed using a 3-step procedure: (i) acetone, (ii) isopropanol, and (iii) demineralized water. The anodization was carried out at room temperature in a conventional two-electrode cell using a direct current (DC) power supply (Figure 2). Ti foil (working electrode) was connected as an anode, and platinum (Pt) electrode (counter electrode) was connected as a cathode. Ti foil was pressed with the o-ring in the electrochemical cell and the area exposed to the electrolyte was 1 cm². The anodization was performed in an electrolyte of mass composition 1.2% NH₄F, 2% demineralized water in EG at 30 V, for 30 min. Details of chemical reactions and phenomena that occur during the process have already been explained³⁷. After anodization, the samples were immediately washed with ultrapure water and dried in nitrogen stream. As-prepared TiO₂ films were amorphous. Stable anatase phase was obtained by thermal annealing. Annealing was car-

ried out in a tube furnace for 2 h at 500 °C using a ramp rate of 1 °C/min. Decoration of nanostructured TiO₂NT with Au nanoparticles was performed by photoreduction. The prepared TiO₂NT samples were immersed in 0.05 M hydrogen tetrachloroaurate solution (HAuCl₄) and, with constant stirring at 500 rpm, illuminated with UV light for 4 h. After 4 h, samples 1 and 2 were washed with ethanol and deionized water. Samples TiO₂NT/Au 1 and TiO₂NT/Au 2 were prepared.

Instrumentation

Anodization was done with the device DC power supply DF 1731 SBO (V&A Instrument, China). Raman spectroscopy (RS) measurements were performed using a Horiba/Jobin-Yvon T64000 spectrometer (Villeneuve D'Ascq, France) with a Coherent Innova 400 (Santa Clara, CA, USA) argon-ion laser operating at 514.5 nm for the excitation. The Raman data were collected with a multi-channel CCD detector. The morphology of the surface and chemical composition of the samples were examined with a field emission gun scanning electron microscopy (FEG-SEM) device JEOL model 7000F equipped with an energy dispersive spectroscopy (EDS) system.

Photocatalytic experiments were performed in a flow cell ($d = 4.5$ cm, $h = 2$ cm) connected to a peristaltic pump ($q = 67$ mL min⁻¹). Photocatalytic film foils were placed on the bottom of the cell so that the photocatalyst stood perpendicular to the light radiation³⁸. Prior to the experiments, solution E2 ($c_0(\text{E2}) = 0.3$ mmol dm⁻³) was recirculated through a system in the dark to achieve adsorption balance of the analyte on the photocatalyst (lamps are lit at $t = 0$ min). The radiation sources were: (i) a full-spectrum fluorescent lamp simulating solar radiation (Exo Terra, 20W) and (ii) an incandescent lamp emitting only visible light (Osram daylight, 100 W). The change in E2 concentration over time from both sources was monitored on the two photocatalysts prepared in the same manner, using the LC analyses. The LC analysis was done using Knauer HPLC system with fluorescence (FLD) detector and C18 column (150 mm $\times$ 4.60 mm, particle size 4 μ m). The analysis was done using eluent A (0.01% formic acid in MilliQ water) and eluent B (acetonitrile) in gradient elution mode which started with a 4 min linear gradient from 70% A to 60% B, followed by a 3 min linear gradient to 95% B which was maintained for 6 min and then a 0.1 min linear gradient back to 70% of A; the flow rate was 0.5 mL/min. Detection of E2 in all samples was accomplished at an excitation wavelength of 280 nm and an emission of 310

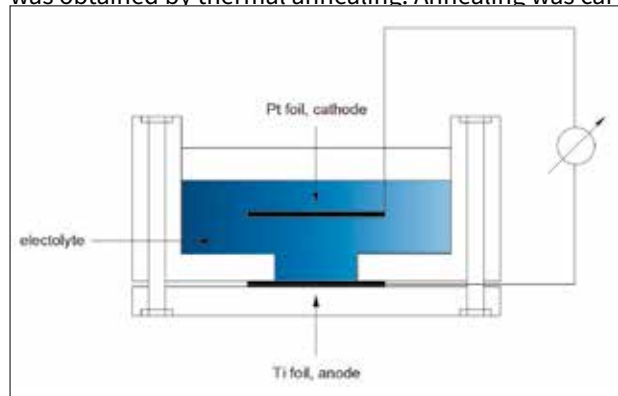


Figure 2. Conventional two-electrode cell.

nm. Fluorescence detector wavelengths were selected based upon literature³⁹.

Results and discussion

Characterisation

Raman spectra of TiO_2NT and $\text{TiO}_2\text{NT}/\text{Au}$ (Figure 3) shows characteristic lines related to the anatase crystal phase⁴⁰. We notice the loss of some spectral lines (designated with arrows), which indicates that the modification of TiO_2NT with Au nanoparticles was successful.

The surface of the TiO_2NT sample is displayed at the magnification of 33,000, 75,000 and 200,000 times respectively (Figures 4, 5 and 6). We observed neat morphology and orderly arrangement of nanotubes. The approximate size of nanotube diameter was determined to be $0.125\ \mu\text{m}$. Figure 7 shows colloidal solution of Au nanoparticles. Approximate nanoparticle diameter was 51 nm, which indicates that particles of this size are easily positioned within TiO_2NT . Figure 8 illustrates the surface of the $\text{TiO}_2\text{NT}/\text{Au}$ sample at the magnification of 100,000 times, where Au nanoparticles are clearly seen. The presence of Au nanoparticles was also confirmed with EDS analysis. Figure 9 demonstrates elementary analysis which established the existence of Ti, O and Au atoms on the sample, which is further evidence of the preparation of $\text{TiO}_2\text{NT}/\text{Au}$.

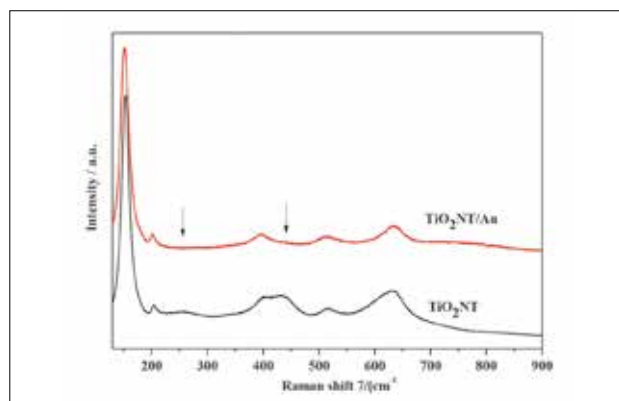


Figure 3. Raman spectra of TiO_2NT and $\text{TiO}_2\text{NT}/\text{Au}$.

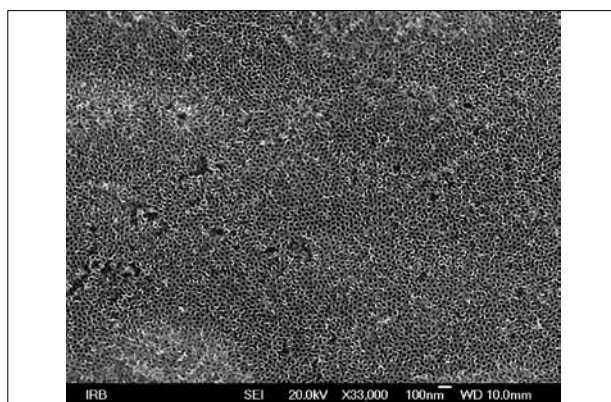


Figure 4. The surface of the photocatalyst TiO_2NT at a magnification of 33.000 times.

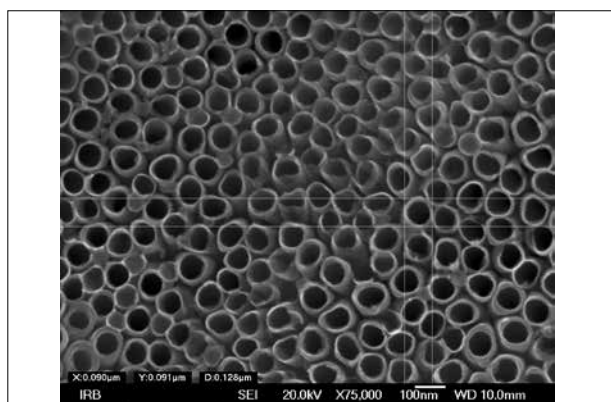


Figure 5. The surface of the photocatalyst TiO_2NT at a magnification of 75.000 times and the approximate size of the nanotube.

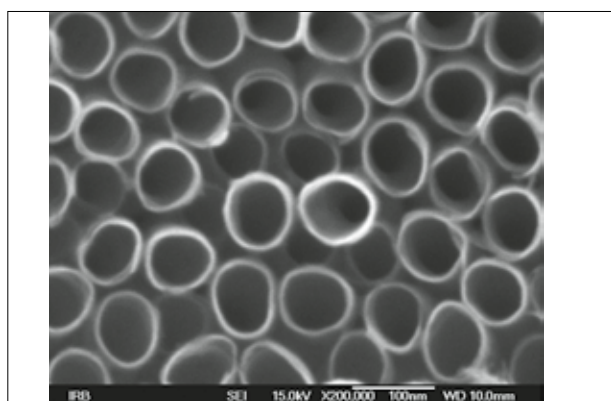


Figure 6. The surface of the photocatalyst TiO_2NT at a magnification of 200.000 times.

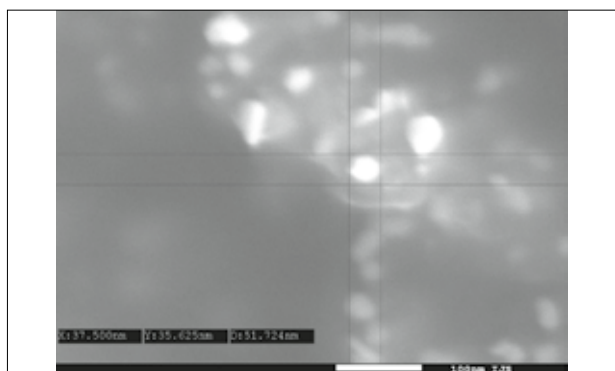


Figure 7. **Colloidal solution of Au nanoparticles.**

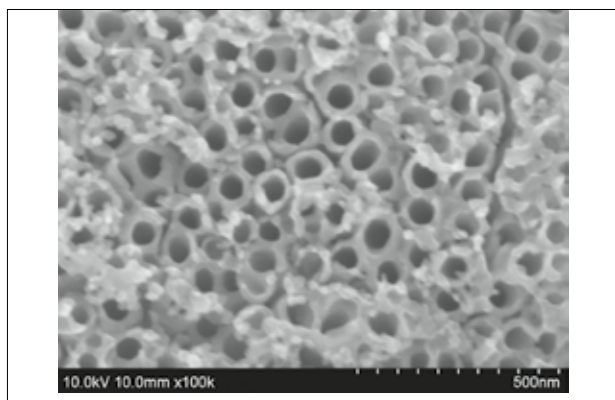


Figure 8. **The surface of the photocatalyst $\text{TiO}_2\text{NT}/\text{Au}$ at a magnification of 100.000 times.**

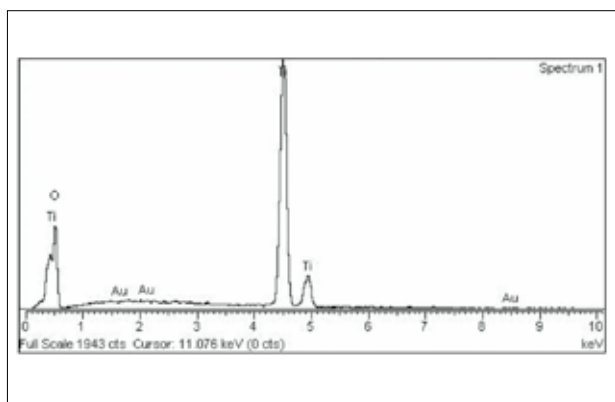


Figure 9. **Elemental analysis (EDS) of photocatalyst $\text{TiO}_2\text{NT}/\text{Au}$.**

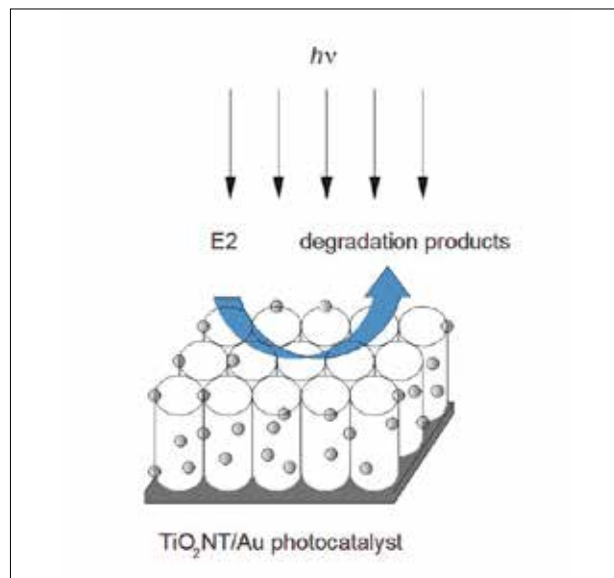


Figure 10. **Schematic representation of photocatalytic degradation of E2.**

Photocatalysis

Schematic representation of photocatalytic degradation of E2 onto $\text{TiO}_2\text{NT}/\text{Au}$ is shown in Figure 10. The kinetics of photocatalytic degradation of E2 under the simulated full spectrum of solar radiation and visible light are shown in Figures 11 and 12 respectively. Photochemical degradation of E2 was observed during simulated solar radiation, which was expected because E2 contains chromophores that make it sensitive to photolysis. However, the photocatalytic degradation of E2 is significantly faster with $\text{TiO}_2\text{NT}/\text{Au}$ with both radiation sources. Kinetic parameters, reaction rate constant (k) for photolysis (decomposition without catalyst) and photocatalytic degradation on TiO_2NT , $\text{TiO}_2\text{NT}/\text{Au}$ 1 and 2 are given in Table 1 for both radiation sources.

The results of E2 degradation show that photolytic degradation due to UV absorption ($\lambda_{\text{max}} \sim 280 \text{ nm}$) is evident at the full spectrum of solar radiation. At the full spectrum, there is a slightly smaller difference between the E2 degradation rate constants without and with catalysts. Sample 2 proved to be the best photocatalyst, which achieved about 1.8 times faster degradation of E2 than photolysis. In visible radiation (with a very low content of UVA part of the radiation) photolysis is almost negligible and the decomposition can be attributed to thermal decomposition rather than photolytic. In this case, sample 1 proved to be better, with which degradation of E2 was about 2.9 times faster than by

photolysis. The differences in photocatalyst samples behaviour can be attributed to different absorption of irradiation at photocatalysts surface, where Sample 1 exhibited higher absorption in the visible region of applied irradiation.

Table 1. E2 degradation rate constants in a flow cell with TiO ₂ NT and TiO ₂ NT/Au.			
full spectrum of solar radiation		visible light	
sample	k x 10 ⁻² , min ⁻¹	sample	k x 10 ⁻³ , min ⁻¹
-*	2.60	-*	2.41
TiO ₂ NT	3.81	TiO ₂ NT	4.19
TiO ₂ NT/Au 1	3.70	TiO ₂ NT/Au 1	7.02
TiO ₂ NT/Au 2	4.79	TiO ₂ NT/Au 2	6.66

*only photolysis of E2 due to radiation absorption was observed in the experiment

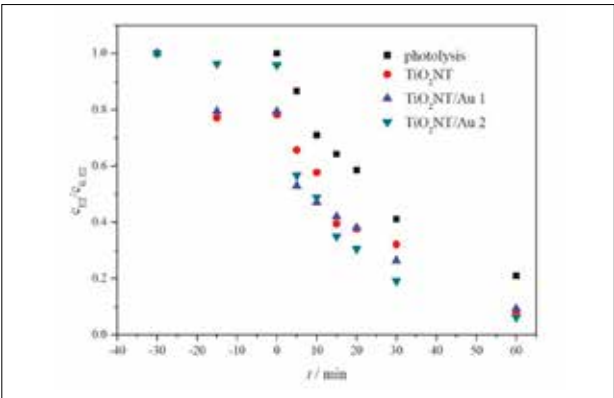


Figure 11. Kinetics of photolysis and photocatalytic degradation of E2 with the full spectrum of solar radiation.

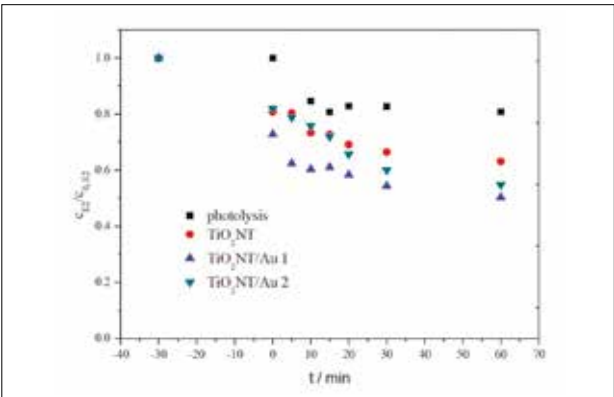


Figure 3. Raman spectra of TiO₂NT and TiO₂NT/Au.

Conclusion

The prepared photocatalyst TiO₂NT/Au was characterized and its photocatalytic activity in model E2 solution was tested. The results indicate the ability of the catalyst to absorb radiation of the visible part of the spectrum and pronounced photocatalytic activity. TiO₂NT/Au presents a promising platform for future research in wastewater treatment since it enables employment of renewable energy sources.

References

1. Bavykin DV, Walsh FC. Titanate and Titania Nanotubes Synthesis, Properties and Applications; Roy. Soc. Ch. 2009.
2. Kuchibhatla SVNT, Karakoti AS, Bera D, Seal S. One dimensional nanostructured materials. Prog. Mater. Sci. 2007 July;52(5):699-913.
3. Roduner E. Size matters: why nanomaterials are different. Chem. Soc. Rev. 2006 May;35(7):583-92.
4. Arico AS, Bruce PG, Scrosati B, Tarascon JM, van Schalkwijk W. Nanostructured materials for advanced energy conversion and storage devices. Nat. Mater. 2005 May;4(5): 366-77.
5. Bruce PG, Scrosati B, Tarascon JM. Angew. Chem.-Int. Edit. 2008 Apr;47(16):2930-46.
6. Tuantranont A, editor. Applications of Nanomaterials in Sensors and Diagnostics. Springer-Verlag Berlin Heidelberg; 2013, 285 p.
7. Gratzel M. Dye-sensitized solar cell., J. Photochem. Photobiol. C-Photochem. Rev. 2003;4(2):145-53.
8. Hagfeldt A, Boschloo G, Sun L, Kloo L, Pettersson H. Dye-sensitized solar cells. Chem. Rev. 2010 Sept;110(11):6595-663.
9. Galstyan V, Comini E, Faglia G, Sberveglieri G. TiO₂ nanotubes: recent advances in synthesis and gas sensing properties. Sensors. 2013 Oct;13(11):14813-38.
10. Fujishima A, Rao TN, Tryk DA. Titanium dioxide photocatalysis., J. Photochem. Photobiol. C-Photochem. Rev. 2000 Jun;1(1):1-21.
11. Xi JQ, Schubert MF, Kim JK, Schubert EF, Chen M, Lin SY, Liu W, Smart JA. Optical thin-film materials with low refractive index for broadband elimination of Fresnel reflection. Nat. Photonics. 2007 Mar;1(3):176-9.

12. Liu XY, Chu PK, Ding C. Surface modification of titanium, titanium alloys, and related materials for biomedical application. *Mater. Sci. Eng. R-Rep.* 2004 Dec;47(3-4):49-121.
13. Hulteen JC, Martin CR. A general template-based method for the preparation of nanomaterials, *J. Mater. Chem.* 1997;7(7):1075-87.
14. Kasuga T, Hiramatsu M, Hoson A, Sekino T, Niihara K. Formation of Titanium Oxide Nanotube, *Langmuir.* 1998 May 23;14(12):3160-3.
15. Chen Q. Trititanate Nanotubes Made via a Single Alkali Treatment. *Adv. Mater.* 2002 Aug 29;14(17):1208.
16. Gong D, Grimes AC, Varghese OK, Hu W, Singh RS, Chen Z, Dickey EC. Titanium oxide nanotube arrays prepared by anodic oxidation. *J. Mater. Res.* 2001;16(12):3331-4.
17. Mor GK, Varghese OK, Paulose M, Grimes CA. Transparent Highly Ordered TiO₂ Nanotube Arrays via Anodization of Titanium Thin Films. *Adv. Funct. Mater.* 2005 July;15(8):1291.
18. Macak JM, Tsuchiya H, Taveira L, Aldaberggerova S, Schmuki P. Smooth Anodic TiO₂ Nanotubes. *Angew. Chem.-Int. Edit.* 2005 Nov;44(45):7463.
19. Beranek R, Hildebrand H, Schmuki P. Self-Organized Porous Titanium Oxide Prepared in H₂SO₄/HF Electrolytes. *Electrochem. Solid State Lett.* 2003 Jan;6(3):B12.
20. Zwilling V, Aucouturier M, Darque-Ceretti E. Anodic oxidation of titanium and TA6V alloy in chromic media. An electrochemical approach. *Electrochim. Acta* 1999 Dec;45(6):921-9.
21. Ghicov A, Schmuki P. Self-ordering electrochemistry: a review on growth and functionality of TiO₂ nanotubes and other self-aligned MO_x structure. *Chem. Commun.* 2009;(20):2791.
22. Bauer S, Kleber S, Schmuki P. TiO₂ nanotubes: Tailoring the geometry in H₃PO₄/HF electrolytes. *Electrochem. Commun.* 2006 Aug;8(8):1321-5.
23. Macak JM, Tsuchiya H, Schmuki P. High-Aspect-Ratio TiO₂ Nanotubes by Anodization of Titanium, *Angew. Chem.-Int. Edit.* 2005 Mar;44(14):2100.
24. Albu SP, Ghicov A, Macak JM, Schmuki P. 250 µm long anodic TiO₂ nanotubes with hexagonal self-ordering. *Phys. Status Solidi-Rapid Res. Lett.* 2007 Nov;1(2):R65.
25. Paulose M, Prakasham HE, Varghese OK, Peng L, Popat KC, Mor GK, Desai TA, Grimes CA. TiO₂ Nanotube Arrays of 1000 µm Length by Anodization of Titanium Foil: Phenol Red Diffusion. *J. Phys. Chem. C* 2007 Sep;111(41):14992-7.
26. Roy P, Schmuki P. TiO₂ Nanotubes: Synthesis and Applications. *Angew. Chem.-Int. Edit.* 2011 Mar;50(13):2904.
27. 2Ali G, Chen C, Hwa Yoo S, Min Kum J, Oh Cho S. Fabrication of complete titania nanoporous structures via electrochemical anodization of Ti. *Nanoscale Res. Lett.* 2011 Apr 13;6.
28. Grimes CA, Mor GK. *TiO₂ Nanotube Arrays: Synthesis, Properties, and Applications.* Springer US; 2009.
29. Cai QY, Paulose M, Varghese OK, Grimes CA. The Effect of Electrolyte Composition on the Fabrication of Self-Organized Titanium Oxide Nanotube Arrays by Anodic Oxidation. *J. Mater. Res.* 2005 Jan;20(1):230-6.
30. Mor GK, Shankar K, Paulose M, Varghese OK, Grimes CA. Enhanced Photocleavage of Water Using Titania Nanotube Arrays. *Nano Lett.* 2005;5(1):191-5.
31. Paulose M, Shankar K, Yoriya S, Prakasham HE, Varghese OK, Mor GK, Latempa TA, Fitzgerald A, Grimes CA. Anodic Growth of Highly Ordered TiO₂ Nanotube Arrays to 134 µm in Length. *J. Phys. Chem. B.* 2006;110(33):16179-84.
32. Suhail MH, Rao GM, Mohan S. dc reactive magnetron sputtering of titanium-structural and optical characterization of TiO₂ films. *J. Appl. Phys.* 1992;71(3):1421.
33. Zahra Z, Habib Z, Chung S, Badshah MA. Exposure Route of TiO₂ NPs from Industrial Applications to Wastewater Treatment and Their Impacts on the Agro-Environment. *Nanomaterials (Basel).* 2020 Aug;10(8):1469.
34. Paramasivam I, Jha H, Liu N, Schmuki P. A review of photocatalysis using self-organized TiO₂ nanotubes and other ordered oxide nanostructures. *Small.* 2012 Oct 22;8(20):3073-103.
35. Directive 2013/39/EU of The European parliament and of the Council on the amending Directives 2000/60/EC and 2008/105/EC as regards priority substances in the field of water policy. *Official Journal. OJ L* 226. 9 p. <https://ec.europa.eu/environment/pubs/pdf/factsheets/7eap/hr.pdf>.
36. Mandić V, Plodinec M, Kereković I, Jurać K, Janicki V, Gracin D, Gajović A, Moguš-Milanković A, Willinger MG. Tailoring anatase nanotubes for the photovoltaic device by the anodization process on behalf of microstructural features of titanium thin film. *Sol. Energy Mater Sol. Cells.* 2017;168:136-45.
37. Grčić I, Brnardić I, Mutavdžić Pavlović D, Mandić V, Papić S. Photocatalytic Activity of Synthesized Titanate Nanotubes and Nanoribbons vs. Commercial TiO₂ under Artificial Solar and Visible Irradiation using 17β-Estradiol as Model Micropollutant. *Desalin. Water Treat.* 2017;67:300-8.
38. Grčić I, Brnardić I, Mutavdžić Pavlović D, Mandić V, Papić S. Photocatalytic activity of synthesized titanate nanotubes and nanoribbons vs. commercial TiO₂ under artificial solar and visible irradiation using 17β-estradiol as model micropollutant. *Desalin. Water Treat.* 2017;67:300-8.
39. Ohsada T, Izumi F, Fyiki Y. Raman Spectrum of Anatase, TiO₂. *J. Raman Spec.* 1978;7(6):321-4.



Nanomaterijal TiO₂/Au za fotokatalitičku razgradnju hormona

¹ Irena Kereković

² Ivana Grčić

³ Andreja Gajović

¹ Zdravstveno veleučilište Zagreb

² Geotehnički fakultet Sveučilišta u Zagrebu, Zavod za inženjerstvo okoliša, Zagreb

³ Institut Ruđer Bošković, Zagreb

Sažetak

Pripremljen je fotokatalizator na bazi nanocjevčica TiO₂ dopiranih nanočesticama Au. Za osnovnu karakterizaciju nanostruktura primijenjena je Ramanova spektroskopija, koja je potvrdila anatas kristalnu fazu fotokatalizatora TiO₂ i prisutnost Au na površini. Morfologija površine na nanoskali i kemijski sastav uzoraka ispitani su skenirajućom elektronskom mikroskopijom (FEG-SEM) opremljenom sustavom energetske disperzivne spektroskopije (EDS), što je potvrdilo pripremu TiO₂NT/Au. Fotolitička i fotokatalitička degradacija estrogenog hormona 17-beta-estradiola (E2) u širokom rasponu valnih duljina ulaznog zračenja (300 do 1100 nm) ukazuju na sposobnost novosintetiziranog katalizatora da apsorbira zračenje vidljivog dijela spektra i izraženu fotokatalitičku aktivnost.

Ključne riječi: nanostrukturirani TiO₂, nanočestice Au, fotokataliza, hormoni